



# Process Optimization for Development of Edible Plates Using By-products of Rice and Dhal Processing Industries

Gouthami, N. S. <sup>a\*</sup>, Mathad, P. F. <sup>a</sup>, Udaykumar Nidoni. <sup>a</sup>,  
Sharanagouda Hiregoudar <sup>a</sup> and Nagaraj, M. Naik <sup>a</sup>

<sup>a</sup> Department of Processing and Food Engineering, College of Agricultural Engineering, Raichur, University of Agricultural Sciences, Raichur-584104, India.

## Authors' contributions

This work was carried out in collaboration among all authors. All authors read and approved the final manuscript.

## Article Information

DOI: <https://doi.org/10.9734/acri/2024/v24i11954>

## Open Peer Review History:

This journal follows the Advanced Open Peer Review policy. Identity of the Reviewers, Editor(s) and additional Reviewers, peer review comments, different versions of the manuscript, comments of the editors, etc are available here: <https://www.sdiarticle5.com/review-history/125965>

**Original Research Article**

**Received: 05/08/2024**  
**Accepted: 31/10/2024**  
**Published: 05/11/2024**

## ABSTRACT

Edible plates can be used as utensils to serve solids, semi-solids and highly viscous liquid food products which are made out of food grains and are filled with various nutrients without any added preservatives. Edible plates from the rice bran flour (RBF), pigeonpea broken flour (PBF) and wheat flour (WF) were prepared by mixing in different proportions viz., 10, 15 and 20% of RBF, 20, 25 and 30% of PBF and the remaining proportion WF as the base material. Objective of this work is to evaluate the quality characteristics of developed edible plates. The optimized treatment was obtained with 20% of RBF, 30% of PBF and WF of 50%. The hardness and fracturability of the was found to be maximum (25.46 and 12.79 N) in T<sub>9</sub>. The tensile strength and elongation at break was also more in treatment T<sub>9</sub> of 3.36 MPa and 2.13%. The tensile strength and elongation at break increased with the increase in supplementation level of by-products.

\*Corresponding author: Email: [gouthaminayak.18@gmail.com](mailto:gouthaminayak.18@gmail.com);

**Cite as:** N. S., Gouthami, Mathad, P. F., Udaykumar Nidoni., Sharanagouda Hiregoudar, and Nagaraj, M. Naik. 2024. "Process Optimization for Development of Edible Plates Using By-Products of Rice and Dhal Processing Industries". *Archives of Current Research International* 24 (11):121-27. <https://doi.org/10.9734/acri/2024/v24i11954>.

**Keywords:** Edible plates; composite flour; rice bran flour; fracturability; hardness.

## ABBREVIATIONS

*PBF* : Pigeonpea Brokens Flour  
*RBF* : Rice Bran Flour  
*TPA* : Texture Profile Analysis  
*WF* : Wheat Flour

## 1. INTRODUCTION

India is one of the largest producer of food grains and stands among top three in terms of production of various agricultural commodities like paddy, wheat, pulses, groundnut, rapeseeds, fruits, vegetables, sugarcane, tea, jute, cotton, tobacco leaves, etc. The total food grain production in India is estimated as 283.37 million tonnes during the year 2018-19 as compared to 277.49 million tonnes in the previous year. Among the food grains, the production of cereals account for 260.15 million tonnes. The production of rice, wheat and pulses were 115.6, 99.12 and 24.02 million tonnes, respectively during 2018-19 (Anon., 2019).

In India, rice is being processed in well established rice milling industries. The major by-products of rice milling industry are rice husk (20-22%) and rice bran (8-10%). Rice bran is a good source of proteins, minerals, fibre and fatty acids. Rice bran proteins are rich in essential amino acids specially lysine (Gul et al., 2015). In rice bran, plenty of other nutrients and active compositions, such as non-starch polysaccharides, phenolic acids, flavonoids, tocopherols, tocotrienols, c-oryzanol and phytic acid (Goufo and Trindade, 2014). Baked products such as cookies, muffins, pastries have all shown a better nutritional value with the use of rice bran flour (Alauddina et al., 2017). Pigeonpea is the second largest pulse crop accounting for about 20% of total pulse production in India. During the processes of dhal milling, the losses due to powder and broken are estimated to be about 10-15%. The broken dhal has got very less commercial value in the market. These broken dhal have a good potential for usage in the preparation of different value added products (Anon., 2016). With increased urbanization, most of the people are stepping out for jobs, they are having hardly any time for cooking and washing utensils. In fast food restaurants, canteens, town festivals, sport events and feasts, etc., disposable tableware is distributed to the restaurant guests in place of

traditional durable tableware in order to simplify management and avoid washing-up (Patil and Sinhal, 2018).

Utensils used in our routine life are cups, bowls, cutleries, bottles, etc. Generally, utensils and cutleries are made of silver, steel, aluminum, brass, copper or any other alloy, wood or plastics, etc. Plastic waste is dangerous to the human health as it contains several hazardous chemical complexes and carcinogens that may leach into the food (Gautham and Caetano, 2017). Therefore, there is always a need for an alternative to these plastic cutleries. Biodegradable and edible cutleries are eco-friendly and also easily disposable. Biodegradable cutleries are made from different sustainable resources like plant based materials like banana, areca, tapioca, sugarcane bagasse, etc. The biodegradable articles inventions are largely based on injection or extrusion methods of production, which are energy intensive processes. To overcome the difficulties in the production of biodegradable cutleries, there is a need to search for an alternative processes or products (Anu et al., 2012).

One of the possible way to utilise the broken dhal and rice bran could be in the preparation of edible cutleries to enhance its nutritional value. Edible cutleries have created a storm interest in various countries to adopt smarter, safer and cleaner substitutes for single use plastic and biodegradable cutleries (Rashid, 2019). Edible cutleries can be used as utensils to serve solids, semi-solids and highly viscous liquid food products (Woods and Martel, 2002). Generally, the edible cutleries are made of food grains and are filled with various nutrients without any added preservatives. These are environment friendly which can be discarded and decomposed easily (Anu et al., 2012).

## 2. MATERIALS AND METHODS

The raw materials viz., rice bran and pigeonpea brokens were procured from local rice and dhal mill. Wheat flour was procured from the local market. These selected by-products were cleaned and ground to fine powder. The flour samples were passed through the sieve No. 170 and obtained particle size of 88-90  $\mu\text{m}$  (Ahmed et al., 2016).

## 2.1 Quality Parameters of Developed Edible Plates

The composite flour for the development of edible plates were prepared by mixing rice bran flour (10, 15, 20%), pigeonpeabrokens flour (20, 25, 30%) and wheat flour as the base material. The treatment details are shown in Table 1. The process flow chart for the development of edible plates is shown in Fig. 1. Guar gum powder and water were added to the flour mixture. A chapathi making roller was used to knead the dough (60 g). The kneaded dough was placed in the plate mould and baked for 15 minutes in the deck oven at  $180\pm 5^{\circ}\text{C}$ . The edible plate made from only wheat flour was considered as control. The prepared edible plate were cooled to a room temperature ( $30\pm 2^{\circ}\text{C}$ ) and packed in polyethylene bag until further analysis.


## 2.2 Texture Profile Analysis (TPA)

Textural qualities of edible plates were measured with this device Textural Analyzer (M/s. Stable Micro Systems, TA.XT Plus/TA.HD, Vienna court, UK). The texture analyzer (TA) was a microprocessor controlled analysis system, which could be interfaced to a wide range of peripherals, including PC-type computers. The

texture analyzer measured force, distance, and time in a most basic test, thus providing three dimensional product analysis. Forces could be measured against set distances and distances may be measured to achieve set forces. The probe carrier contained a very sensitive load cell. The TA.HD plus load cell had electronic overload protection. The TA.XT plus load cell had mechanical overload. The analyzer was linked to a computer that recorded the data via software program Stable Micro System Exponents software.

**Table 1. Treatment combinations of composite flour with selected proportions of rice bran flour (RBF), pigeonpeabrokens flour (PBF) and wheat flour (WF)**

Treatment	Details of the treatment
T <sub>0</sub>	100% WF
T <sub>1</sub>	10% RBF + 20% PBF + 70% WF
T <sub>2</sub>	10% RBF + 25% PBF + 65% WF
T <sub>3</sub>	10% RBF + 30% PBF + 60% WF
T <sub>4</sub>	15% RBF + 20% PBF + 65% WF
T <sub>5</sub>	15% RBF + 25% PBF + 60% WF
T <sub>6</sub>	15% RBF + 30% PBF + 55% WF
T <sub>7</sub>	20% RBF + 20% PBF + 60% WF
T <sub>8</sub>	20% RBF + 25% PBF + 55% WF
T <sub>9</sub>	20% RBF + 30% PBF + 50% WF

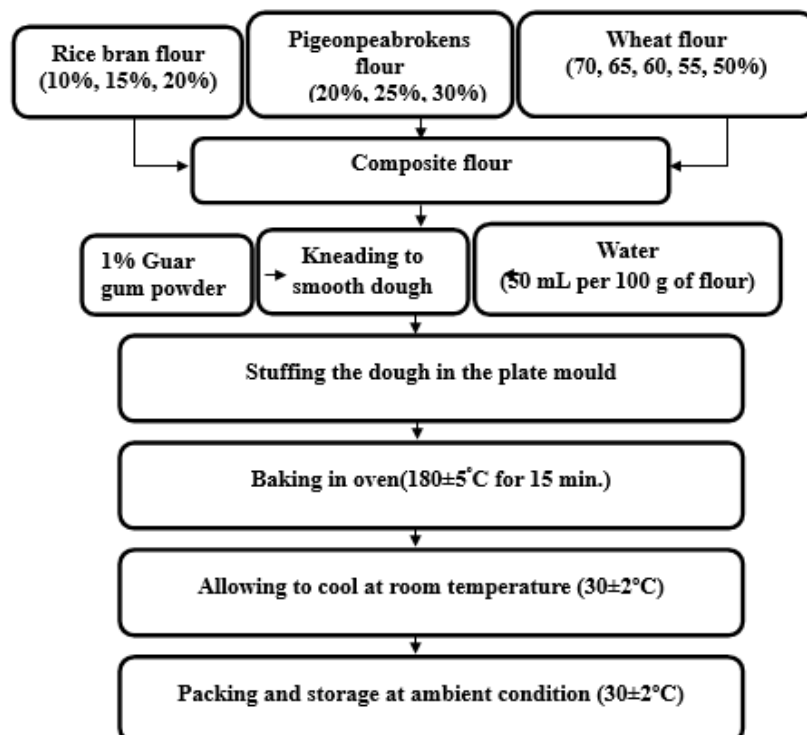

**Fig. 1. Process flow chart for the development of edible plates**

The experiments were carried out by different tests that generated plot of force (g) vs. time(s), from which texture values for edible plates were obtained. Three replications of each combination were taken for analysis. During the testing, the samples were held manually against the base plate and the different tests were applied according to TA settings. The textural properties such as hardness and fracturability were measured by using compression test. The ball probe was used to measure the compression test with the pre-test speed, test speed and post-test speed of 1.0, 1.0 and 10.0 mm/s, respectively (Panghal et al., 2019).

### 2.3 Tensile Strength

The tensile strength of a material is the maximum amount of tensile (pulling) stress that it can take before failure, such as breaking or permanent deformation. The tensile strength of developed edible plates was calculated. The texture analyzer (Stable micro systems, TA.XT Plus/TA.HD, Vienna court, UK) with a 5 kg load cell equipped with tensile grips was used to measure the tensile strength (TS) of developed edible plates according to ASTM D-882 standard. Edible plate sample size of 70 mm x 20 mm was used for the experiment. Grip separation was set at 50 mm, pre-test speed of 2 mm/s, test speed of 1 mm/s and post test speed of 2 mm/s with a cross-head speed of 1.00 mm/s (Barros, 2010 and Ojagh et al., 2010). Tensile strength of edible plates were calculated by using the following formula.

$$\text{Tensile strength} = \frac{F}{L \times W} \quad (1)$$

Where,

TS = Tensile strength (MPa)  
 F = Tension at break (N)  
 L = Length of plate (mm)  
 W = Width of plate (mm)

### 2.4 Elongation at Break

Elongation at break is the measure of materials ductility. This measurement shows how much a material can be stretched, as a percentage of its original dimensions, before it breaks. The ductility of a material depends largely on its chemical composition. Elongation at break of developed edible plates was determined by using textural analyser. Elongation at break ( $E_b$ ) of developed edible plates was calculated by using the following formula (Ojagh et al., 2010).

$$\text{Elongation at break (\%)} = \frac{L_b}{L_o} \times 100 \quad (2)$$

Where,

$E_b$  = Elongation at break (%)  
 $L_b$  = Length of edible plate at break (mm)  
 $L_o$  = Original length of edible plate (mm)

## 3. RESULTS AND DISCUSSION

The results of hardness, fracturability, tensile strength and elongation at break are presented in Table 2.

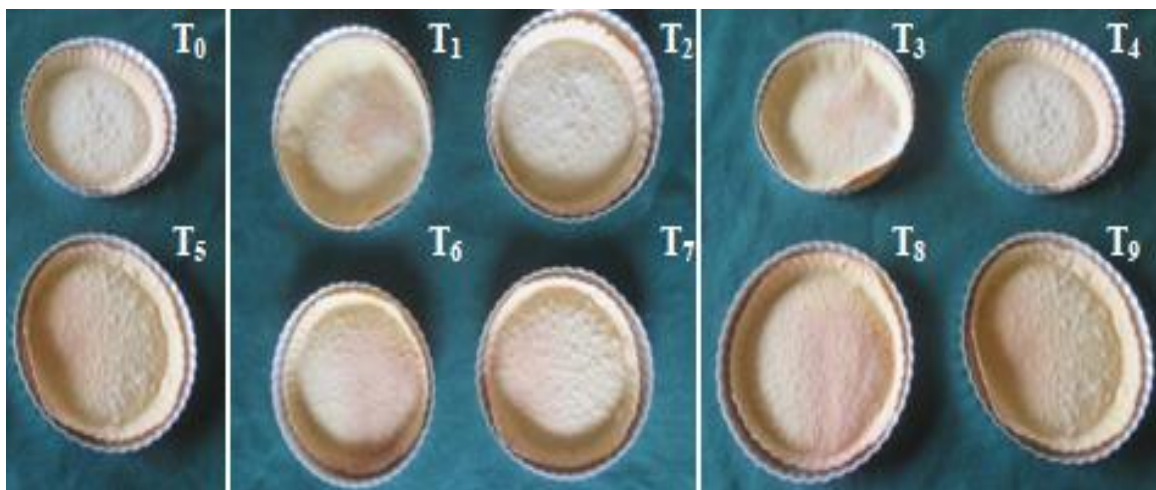


Plate 1. Developed edible plates

### 3.1 Textural Properties of the Developed Edible Plates and Spoons

Texture Profile Analysis (TPA) was carried out for the developed edible plates. The textural properties of developed edible plates, like hardness and fracturability were analysed and are presented in Table 2.

#### 3.1.1 Hardness

The texture analyser was used to determine the hardness of edible plates, and the results are shown in Table 2. The maximum hardness value of edible plate (25.46 N) was discovered in treatment T<sub>9</sub>, whilst the minimum hardness value (23.18 N) was reported in treatment T<sub>1</sub>. The control edible plate (T<sub>0</sub>) was determined to have a hardness of 22.87 N. This could be owing to the high fibre and protein content in the by-products flour utilised in the edible plate creation, which increased the hardness. The results are in good agreement with the findings of Bock et al. (2013) for bread; Jiang et al. (2019) for baked protein enriched corn chips.

#### 3.1.2 Fracturability

Fracturability is the measure of force at which the product started to break. Table 2 displays the fracturability of the edible plates. It was discovered that the fracturability value increased from 11.08 to 12.79 N. Among the treatment combinations, the fracturability value

of the edible plate was found to be maximum (12.79 N) in the treatment T<sub>9</sub>, whereas the minimum (11.08 N) was in the treatment T<sub>1</sub>. The fracturability of control edible plate (T<sub>0</sub>) was found to be 10.57 N. It was discovered that the fracturability value improved when the percentage of by-products viz., rice bran flour and pigeonpea brokens flour increased. This could be owing to the usage of by-products with higher fibre content, which reduces the gluten content of wheat flour used in the creation of edible cutlery. Wheat flour, on average, requires less compression and penetration force than composite flour. The similar results were noticed by Divyashree et al. (2016) for buckwheat and chia seeds fortified biscuits and by Gonzalez et al. (2018) for baked biscuits.

#### 3.1.3 Tensile strength

The tensile strength of a material is the maximum amount of tensile (pulling) stress that it can take before failure, such as breaking or permanent deformation. Table 2 shows the tensile strength of the developed edible plates. The tensile strength of edible plates varied in the range from 2.95 to 3.36 MPa, according to the table. Among the different treatment, The tensile strength of edible plates was found to be highest (3.36 MPa) in treatment T<sub>9</sub> and lowest (2.95 MPa) in treatment T<sub>1</sub>. The tensile strength of control edible plate (T<sub>0</sub>) was found to be 2.87 MPa. It is evident that, as the percentage of the composition of by-products viz., rice bran flour

Table 2. Textural properties of developed edible plates

Treatment	Hardness (N)	Fracturability (N)	Tensile strength (MPa)	Elongation at break (%)
T <sub>0</sub>	22.87	10.57	2.87	1.72
T <sub>1</sub>	23.18	11.08	2.95	1.78
T <sub>2</sub>	23.52	11.29	3.21	1.81
T <sub>3</sub>	23.97	11.41	3.22	1.82
T <sub>4</sub>	24.05	11.62	3.25	1.83
T <sub>5</sub>	24.27	11.85	3.27	1.87
T <sub>6</sub>	24.58	12.16	3.28	2.02
T <sub>7</sub>	24.97	12.34	3.33	2.05
T <sub>8</sub>	25.13	12.58	3.35	2.09
T <sub>9</sub>	25.46	12.79	3.36	2.13
Mean	23.35	11.77	3.21	1.91
SE(m) ±	0.232	0.259	0.073	0.043
CD @ 1 %	0.943	1.054	0.297	0.174

T<sub>0</sub>-Control edible plates (100% WF), T<sub>1</sub>-Edible plates (10% RBF+20% PBF + 70% WF), T<sub>2</sub>-Edible plates(10% RBF+25% PBF + 65% WF), T<sub>3</sub>-Edible plates(10% RBF+30% PBF+ 60% WF), T<sub>4</sub>-Edible plates(15% RBF+20% PBF+65% WF), T<sub>5</sub>-Edible plates(15% RBF+25% PBF + 60% WF), T<sub>6</sub>-Edible plates(15% RBF+30% PBF+55% WF), T<sub>7</sub>-Edible plates(20% RBF+20% PBF + 60% WF), T<sub>8</sub>-Edible plates(20% RBF+25% PBF + 55%WF) and T<sub>9</sub>-Edible plates(20% RBF+30% PBF + 50% WF)

and pigeonpeabrokens flour increased, the tensile strength of the edible plate went on increasing. The results are in good agreement with the findings of Snijder et al. (2003) for biodegradable plates made from wheat bran and by Barros (2010) for the whole and refined wheat flour tortilla.

#### 3.1.4 Elongation at break

Elongation at break is the measure of materials ductility. This measurement shows how much a material can be stretched, as a percentage of its original dimensions, before it breaks. The ductility of a material depends largely on its chemical composition. The elongation at break of the developed edible plates are presented in Table 2. Among the different treatments, the elongation at break of the developed edible plate was recorded to be maximum (2.13%) in the treatment T<sub>9</sub> whereas, the minimum (1.78%) was recorded in the treatment T<sub>1</sub>. The elongation at break of control edible plate (T<sub>0</sub>) was found to be 1.72%. This might be due to increase in the by-products used in which the composite flour is rich in fibre content. The results are in good agreement with the findings of Barros (2010) for tortilla.

## 4. CONCLUSION

The replacement of wheat flour with rice bran flour up to 20% and 30% pigeonpeabrokens flour is possible without adversely affecting sensory characteristics of edible plates. The textural properties such as hardness, fracturability, tensile strength and elongation at break was more in treatment T<sub>9</sub> (20% RBF+30% PBF). The textural properties increased with the increase in supplementation level of by-products.

### DISCLAIMER (ARTIFICIAL INTELLIGENCE)

Author(s) hereby declare that NO generative AI technologies such as Large Language Models (ChatGPT, COPILOT, etc.) and text-to-image generators have been used during the writing or editing of this manuscript.

### ACKNOWLEDGEMENT

The authors express heartfelt gratitude to the Department of Processing and Food Engineering, College of Agricultural Engineering, University of Agricultural Sciences Raichur, for providing the laboratory facilities and financial support for this work.

## COMPETING INTERESTS

Authors have declared that no competing interests exist.

## REFERENCES

- Ahmed, J., Al-Attar, H., & Arfat, Y. A. (2016). Effect of particle size on compositional, functional, pasting, and rheological properties of commercial water chestnut flour. *Food Hydrocolloids*, 52(8), 888-895.
- Alauddina, M., Islam, J., Shirakawa, H., Koseki, T., & Komaia, A. M. (2017). Rice bran as a functional food: An overview of the conversion of rice bran into a superfood/functional food. *In Tech University Campus Step RiSlavka Krautzeka 83/A51000 Rijeka, Croatia*, 28(10), 91-305.
- Anonymous. (2016). Pulses in India: Retrospect and prospects. Directorate of Pulses Development, Department of Agriculture Cooperation and Farmers Welfare (DAC and FW), Ministry of Agriculture and Farmers Welfare, Government of India.
- Anonymous. (2019). Indiastat.com, Agricultural production.
- Barros, D. F. R. (2010). Wheat flour tortilla: Quality prediction and study of physical and textural changes during storage (Doctoral dissertation, Texas A and M University).
- Bock, J. E., Connelly, R. K., & Damodaran, S. (2013). Impact of bran addition on water properties and gluten secondary structure in wheat flour doughs studied by attenuated total reflectance Fourier transform infrared spectroscopy. *Cereal Chemistry*, 90(4), 377-386.
- Divyashree, K., Kumar, A. K., Sharma, G. K., & Semwal, A. D. (2016). Development and storage stability of buckwheat-chia seeds fortified biscuits. *International Journal of Food and Fermentation Technology*, 6(1), 103-110.
- Durr, A. K., Rayapudi, R. D., & Peesapathy, N. (2012). Eco-friendly and biodegradable edible utensils including cutlery and chopsticks and methods of making them. *World Intellectual Property Organization International Bureau. Patent No: WO 2012/098448 A1*.
- Gautam, A. M., & Caetano, N. (2017). Study, design, and analysis of sustainable alternatives to plastic takeaway cutlery and

- crochery. *Energy Procedia*, 136(5), 507-512.
- Gonzalez, J. D. T., Gallo, R. T., Correa, D. A., Gallo-Garcia, L. A., & Castillo, P. M. (2018). Instrumental assessment of textural parameters of Colombian lemon biscuits. *Colombia: Department of Agroindustrial Engineering, University of Cartagena*, 11(22), 1085-1102.
- Goufo, P., & Trindade, H. (2014). Rice antioxidants: Phenolic acids, flavonoids, anthocyanins, proanthocyanidins, tocopherols, tocotrienols,  $\gamma$ -oryzanol, and phytic acid. *Food Science and Nutrition*, 2(13), 75-104.
- Gul, K., Yousuf, B., Singh, A. K., Singh, P., & Wani, A. A. (2015). Rice bran: Nutritional values and its emerging potential for development of functional food—A review. *Bioactive Carbohydrates and Dietary Fibre*, 6(1), 24-30.
- Jiang, H., Hettiarachchy, N. S., & Horax, R. (2019). Quality and estimated glycemic profile of baked protein-enriched corn chips. *Journal of Food Science and Technology*, 56(6), 2855-2862.
- Ojagh, S. M., Rezaei, M., Razavi, S. H., & Hosseini, S. M. (2010). Development and evaluation of a novel biodegradable film made from chitosan and cinnamon essential oil with low affinity toward water. *Food Chemistry*, 122(1), 161-166.
- Panghal, A., Chhikara, N., & Khatkar, B. S. (2019). Characterisation of Indian wheat varieties for chapati (flat bread) quality. *Journal of the Saudi Society of Agricultural Sciences*, 18(1), 107-111.
- Patil, H. N., & Sinhal, P. (2018). A study on edible cutlery: An alternative for conventional one. *Journal of Hospitality*, 1(4), 45-51.
- Rashid, M. S. (2019). Edible cutleries as sustainable substitute for plastic cutleries (Doctoral dissertation, Brac University).
- Snijder, M., Keijsers, E., Mulder, W., Schennink, G., Dreumel, M. V., & Wevers, M. (2003). Biotrem: Process and product innovations of bran-based material. *Agrotechnological Research Institute*, 41(4), 1-103.
- Woods, R., & Martel, D. (2002). Edible cup and method of making same. *U.S. Patent* 6,423,357.

**Disclaimer/Publisher's Note:** The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of the publisher and/or the editor(s). This publisher and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.

© Copyright (2024): Author(s). The licensee is the journal publisher. This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:

<https://www.sdiarticle5.com/review-history/125965>